


NASA/CR-2000-209837
ICASE Report No. 2000-1

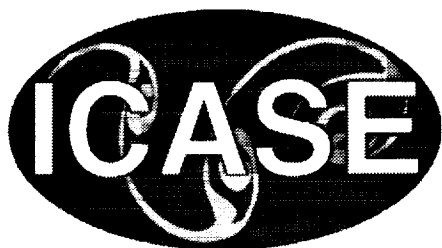

A Model for Asymmetric Hysteresis in Piezoceramic Materials

Ralph C. Smith
North Carolina State University, Raleigh, North Carolina

Zoubeida Ounaies
ICASE, Hampton, Virginia



January 2000

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counter-part or peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.


- **CONFERENCE PUBLICATIONS.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that help round out the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results . . . even providing videos.

For more information about the NASA STI Program Office, you can:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov/STI-homepage.html>
- Email your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA Access Help Desk at (301) 621-0134
- Phone the NASA Access Help Desk at (301) 621-0390
- Write to:
NASA Access Help Desk
NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076-1320

NASA/CR-2000-209837
ICASE Report No. 2000-1

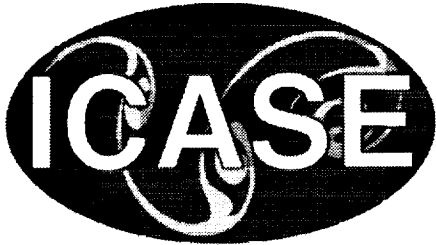

A Model for Asymmetric Hysteresis in Piezoceramic Materials

Ralph C. Smith
North Carolina State University, Raleigh, North Carolina

Zoubeida Ounaies
ICASE, Hampton, Virginia

Institute for Computer Applications in Science and Engineering
NASA Langley Research Center
Hampton, VA

Operated by Universities Space Research Association



National Aeronautics and
Space Administration

Langley Research Center
Hampton, Virginia 23681-2199

Prepared for Langley Research Center
under Contract NAS1-97046

January 2000

Available from the following:

NASA Center for AeroSpace Information (CASI)
7121 Standard Drive
Hanover, MD 21076-1320
(301) 621-0390

National Technical Information Service (NTIS)
5285 Port Royal Road
Springfield, VA 22161-2171
(703) 487-4650

A MODEL FOR ASYMMETRIC HYSTERESIS IN PIEZOCERAMIC MATERIALS

RALPH C. SMITH* AND ZOUBEIDA OUNAIES†

Abstract. This paper focuses on the characterization of hysteresis exhibited by piezoelectric materials at moderate to high field levels. For soft materials in which dipoles are easily reconfigured, the hysteresis loop is observed to be rotationally symmetric about the zero field, zero polarization point and symmetric models can be employed. In harder materials, however, the loops are no longer rotationally symmetric which necessitates the development of commensurate characterization techniques. The model considered here is based upon the quantification of reversible and irreversible changes in polarization due to bending and translation of domain walls pinned at inclusions inherent to the materials. The performance of the model is illustrated through comparison with PZT4 data.

Key words. hysteresis model, piezoceramic materials

Subject classification. Applied and Numerical Mathematics

1. Introduction. An inherent property of piezoelectric materials is the presence of hysteresis and constitutive nonlinearities at moderate to high drive levels. In certain applications, the degree of hysteresis can be minimized by restricting input field or stress levels, or employing certain feedback mechanisms [7]. However, to attain the full capabilities of the materials in high performance applications, it is necessary to quantify the hysteresis and nonlinearities in a manner which permits both material characterization and efficient control design. The latter criterion is facilitated by the development of models which can either be exactly or approximately inverted to permit the construction of inverse compensators for linear control design.

A common form of hysteresis in piezoelectric materials is the sigmoid relation between the input field E and polarization P illustrated in Figure 3.1. For soft materials in which dipoles are easily reversed, the curves are observed to be approximately rotationally symmetric about the point $E = 0$, $P = 0$. For harder materials which are initially poled, the relation is often asymmetric due to the fact that the preferred orientation induced during poling is less easily modified by AC fields at normal operating temperatures. Such a response is illustrated in Figure 3.1a with data from a poled PZT4 wafer. For general applications, it is advantageous to have a model which accommodates both the symmetric unpoled response and asymmetric poled response through the characterization of physical mechanisms which produce the hysteresis. This is accomplished here through the quantification of energy losses which occur when domains reorient and domain walls move in response to an applied field. Details regarding the associated reversible and irreversible domain wall mechanisms can be found in [1, 6].

Various techniques have been employed for modeling hysteresis in piezoelectric materials including macroscopic phenomenological approaches [3, 4, 15], microscopic energy-based models at the lattice or grain level [8], or semi-macroscopic theories which employ energy relations in combination with macroscopic averages

*Center for Research in Scientific Computation, North Carolina State University, Raleigh, NC 27695 (*rsmith@eos.ncsu.edu*). This research was supported by the National Aeronautics and Space Administration under NASA Contract Number NAS1-97046 while this author was a consultant at the Institute for Computer Applications in Science and Engineering (ICASE), M/S 132C, NASA Langley Research Center, Hampton, VA 23681-2199.

† ICASE, M/S 132C, NASA Langley Research Center, Hampton, VA 23681-2199 (*z.ounaies@larc.nasa.gov*). This research was supported by the National Aeronautics and Space Administration under NASA Contract Number NAS1-97046 while this author was in residence at ICASE, M/S 132C, NASA Langley Research Center, Hampton, VA 23681-2199.

to yield models having effective parameters which characterize the bulk behavior of the material [2]. The present model fits in this latter category.

The initial theory underlying this model was developed in [10, 11] for general ferroelectric materials where it was illustrated for PMN at low temperatures. This theory quantifies through electrostatic energy relations the reversible and irreversible effects of domain wall bending and translation. Macroscopic averages then provide a model having five parameters which quantifies the bulk attributes of the material. The extension of this model to piezoelectric compounds and validation for PZT5A was provided in [12]. The initial models and validation results accommodate only symmetric hysteresis loops.

The extension of the model to accommodate asymmetric hysteresis loops of the type depicted in Figure 3.1 is outlined in the next section and then illustrated through a comparison with data from both poled and depoled PZT4 wafers. We note that the basis of the technique on physical mechanisms yields a model in which the effects of poling are accommodated by biases in the field and polarization with the original five hysteresis parameters remaining unchanged. This provides the model with significant flexibility for both material characterization and control design since changes due to poling (or depoling) are incorporated through the physics rather than changes in the model or hysteresis parameters.

2. Model Development. The hysteresis between the electric field E and polarization P is modeled in two steps. In the first, the ideal anhysteretic polarization, which would result in the absence of domain wall pinning, is quantified by employing Boltzmann statistics to determine the probability of dipoles occupying specified energy states. Hysteresis is then incorporated by computing deviations from the anhysteretic state due the restriction of domain wall movement by pinning sites in the material. This approach is motivated by analogous theory for ferromagnetic materials [5]. An analogous model for symmetric hysteresis loops in ferroelectric materials is summarized in [10, 11] with initial validation for piezoelectric materials provided in [12, 13].

To characterize the anhysteretic polarization which would result in the absence of pinning sites, it is necessary to consider the effective field acting on dipoles in the material. In the original symmetric models, the effective field was taken to be

$$E_e = E + \alpha P,$$

where the component αP quantifies the field contributions due to interdomain coupling and certain stress effects. As detailed in [10, 11], the parameter α can be formulated in terms of a scaling electric field \hat{E} and the saturation polarization P_s , but is typically estimated in applications through a least squares fit to data. The asymmetries due to poling are incorporated by noting that they produce a bias field E_0 and bias polarization P_0 which causes the positive and negative coercive fields and remanence points to differ. The resulting effective field is then modeled by

$$(2.1) \quad E_e = (E - E_0) + \alpha(P - P_0).$$

As detailed in [10, 11], the balancing of electrostatic and thermal energy using Boltzmann principles yields a family of models which differ according to assumptions concerning possible domain orientations. In the presence of a scaling polarization P_1 , the assumption that cells can be oriented in any direction yields the Langevin model

$$(2.2) \quad P_{an} = P_1 + P_s \left[\coth \left(\frac{E_e}{a} \right) - \frac{a}{E_e} \right]$$

while the assumption that dipoles can orient only in the direction of the field, or opposite to it, yields the Ising spin model

$$(2.3) \quad P_{an} = P_1 + P_s \tanh\left(\frac{E_e}{a}\right).$$

In both cases, P_s denotes the saturation polarization while a is a parameter which is estimated through a least squares fit to data. Details regarding the behavior of these two models can be found in [10, 11].

Hysteresis is incorporated by computing the irreversible polarization P_{irr} and reversible polarization P_{rev} resulting from the translation and bending of domain walls pinned at inclusions in the material. The quantification of energy required to break pinning sites yields the differential equation

$$(2.4) \quad \frac{dP_{irr}}{dE} = \tilde{\delta} \frac{P_{an} - P_{irr}}{k\delta - \alpha(P_{an} - P_{irr})}$$

specifying the irreversible polarization. The parameter $\delta = \text{sign}(dE)$ ensures that the energy required to break pinning sites always opposes changes in polarization while $\tilde{\delta} = 1$ if $\{dE > 0 \text{ and } P < P_{an}\}$ or $\{dE < 0 \text{ and } P > P_{an}\}$ and $\tilde{\delta} = 0$, otherwise. The parameter k , which quantifies the average energy required to reorient domains, is demonstrated in [13] to be asymptotically approximated by the coercive field E_c in soft materials.

The second component of the polarization is the reversible polarization which models the effects of domain wall bending. To first approximation, this is modeled by the relation

$$(2.5) \quad P_{rev} = c(P_{an} - P_{irr})$$

where c is a parameter which must be estimated for the specific application.


The total polarization is then given by

$$(2.6) \quad P = P_{rev} + P_{irr}.$$


To implement the model, the effective field for a given field and irreversible polarization level is computed using (2.1). This effective field value is then employed in either (2.2) or (2.3) to compute the corresponding anhysteretic polarization. The subsequent irreversible polarization is determined by numerically integrating (2.4). The total polarization is then specified by (2.6).

3. Model Validation. The polarization model (2.6) provides the capability for characterizing hysteresis loops which are either symmetric or asymmetric functions of the input field. To illustrate the performance of the model, we consider the characterization of both poled and unpoled PZT4 wafers. The reported results were obtained from a rectangular wafer having a length of 3.81 cm, width of 0.635 cm and thickness of 0.0381 cm. The wafer was initially poled in the transverse direction.

Input voltages ranging from 600 V to 2200 V were applied to the wafer under thermally controlled conditions and the resulting polarization levels were measured. To minimize frequency effects, the input frequencies were limited to 200 mHz and 1 Hz. While some frequency dependence was noted at 1 Hz, it appears to be manifested primarily in the field attained in the material, and the model performed adequately when the field measured in the material was employed as input. We note that under quasistatic conditions, the field generated in the material by an input voltage V can be approximated by the relation $E = V/d$ where $d = 0.0381$ cm is the thickness of the wafer. The validity of this relation degrades, however, as frequency effects are manifested.

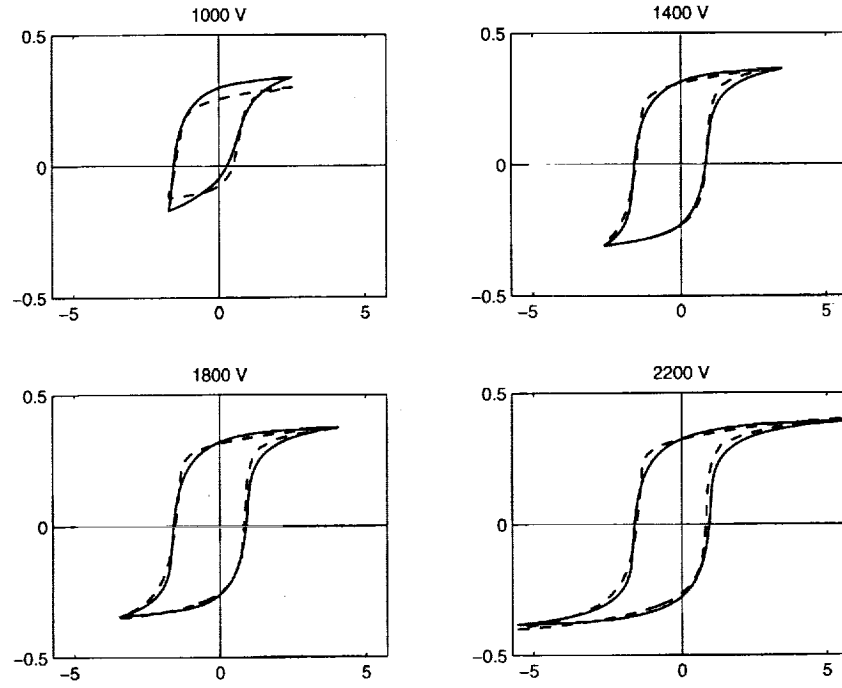

(a) Poled Wafer: Field E versus Polarization P

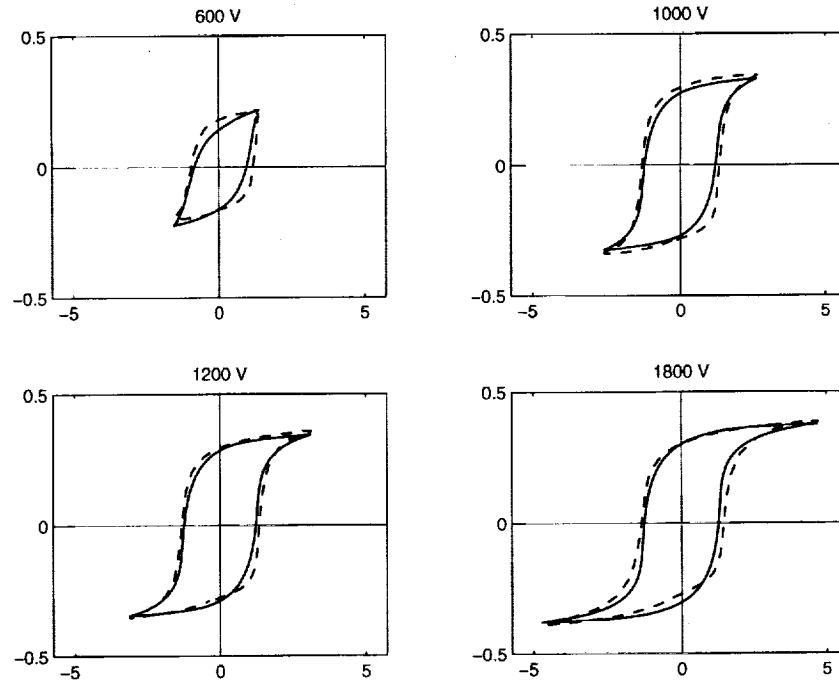

(b) Depoled Wafer: Field E versus Polarization P

FIG. 3.1. Model fit to asymmetric and symmetric PZT4 data with parameters estimated from poled 1 Hz, 2200 V input data; Model (—), Data (---). (a) Fit to 1 Hz data for the poled wafer with $E_0 = -4.0 \times 10^5$, $P_0 = .01$, $P_1 = 0$. (b) Fit to 200 mHz data for the depoled wafer with $E_0 = P_0 = P_1 = 0$.

Initial data sets were collected at 1 Hz under the biased, and hence asymmetric, conditions attributed to poling. The model parameters were estimated through a least squares fit to the 2200 V input data which yielded the values $\alpha = 6.4 \times 10^6$ Vm/C, $a = 8.0 \times 10^5$ C/m², $k = 1.5 \times 10^6$ C/m², $c = 0.5$, $P_s = .44$ C/m² and $E_0 = -4.0 \times 10^5$ V/m, $P_0 = .01$ C/m², $P_1 = 0$. The model, with these parameter values, was then used to predict the hysteresis curves for the material using the measured field values corresponding to 1000 V, 1400 V and 1800 V inputs. The resulting model predictions are compared with the measured data in Figure 1a. It is observed that while the model over-predicts the maximum polarization for the 1000 V input, it characterizes the asymmetry and accurately predicts the hysteresis at the intermediate drive levels.

The wafer was then partially depoled by subjecting it to a sustained high voltage under thermally controlled conditions so that subsequent data was, at least approximately, rotationally symmetric about $E = 0$, $P = 0$ as illustrated in Figure 1b. The model with the *same hysteresis parameters* a, k, c, α, P_s estimated from the poled 1 Hz, 2200 V input data, was then used with the bias values $E_0 = P_0 = P_1 = 0$ to predict the hysteresis in the depoled wafer at various input levels. The data and model behavior for the 1000 V and 1800 V inputs can be compared with those in Figure 1a, and the lower voltage behavior is included to further illustrate the flexibility of the model. We note that while the model fits in Figure 1b can be improved if parameters are refined, the accuracy attained using parameters estimated under different operating conditions attests to the flexibility provided by the incorporation of associated physics in the model.

4. Concluding Remarks. This paper outlines extensions to a domain wall model for piezoelectric materials to accommodate asymmetries due to poling. This modeling strategy is based on the quantification of reversible and irreversible polarization changes due to domain wall pinning at inclusions inherent to the materials. The resulting model has five hysteresis parameters and three field and polarization parameters to incorporate biases due to poling.

The performance of the model was illustrated through a comparison with asymmetric and symmetric PZT4 data collected at several drive levels. The model parameters were estimated through a least squares fit to data collected from the poled wafer at a high drive level and the ensuing model was used to predict both asymmetric and symmetric hysteresis at several drive levels. As illustrated by the model fits, the formulation of the model based on energy principles provides it with the capability for accurately predicting the quasistatic hysteresis curves under varied poling and drive conditions.

Finally, the ODE nature of the model makes it amenable to inversion through the consideration of a complementary ODE in a manner analogous to that described in [9]. This facilitates the construction of an inverse compensator which can be used for linear control design [14].

Acknowledgements. The research of R.C.S. was supported in part by the Air Force Office of Scientific Research under the grant AFOSR-F49620-98-1-0180.

REFERENCES

- [1] I-W. CHEN AND Y. WANG, *A domain wall model for relaxor ferroelectrics*, *Ferroelectrics*, 206 (1998), pp. 245-263.
- [2] W. CHEN AND C.S. LYNCH, *A model for simulating polarization switching and AF-F phase changes in ferroelectric ceramics*, *Journal of Intelligent Material Systems and Structures*, 9 (1998), pp. 427-431.

- [3] W.S. GALINAITIS AND R.C. ROGERS, *Compensation for hysteresis using bivariate Preisach Models*, SPIE Smart Structures and Materials, 1997, Mathematics and Control in Smart Structures, San Diego, CA, 1997.
- [4] P. GE AND M. JOUANEH, *Modeling hysteresis in piezoceramic actuators*, Precision Engineering, 17 (1995), pp. 211-221.
- [5] D.C. JILES AND D.L. ATHERTON, *Theory of ferromagnetic hysteresis*, Journal of Magnetism and Magnetic Materials, 61 (1986), pp. 48-60.
- [6] B.D. LAIKHTMAN, *Flexural vibrations of domain walls and dielectric dispersion of ferroelectrics*, Soviet Physics Solid State, 15(1) (1973), pp. 62-68.
- [7] J.A. MAIN, E. GARCIA AND D.V. NEWTON, *Precision position control of piezoelectric actuators using charge feedback*, Journal of Guidance, Control and Dynamics, 18(5) (1995), pp. 1068-1073.
- [8] M. OMURA, H. ADACHI AND Y. ISHIBASHI, *Simulations of ferroelectric characteristics using a one-dimensional lattice model*, Japanese Journal of Applied Physics, 30(9B) (1991), pp. 2384-2387.
- [9] R.C. SMITH, *Inverse compensation for hysteresis in magnetostrictive transducers*, CRSC Technical Report CRSC-TR98-36; Mathematical and Computer Modeling, to appear.
- [10] R.C. SMITH AND C.L. HOM, *A domain wall model for ferroelectric hysteresis*, SPIE Conference on Mathematics and Control in Smart Structures, SPIE Volume 3667, Newport Beach, CA, March 1-4, 1999, pp. 150-161.
- [11] R.C. SMITH AND C.L. HOM, *A domain wall theory for ferroelectric hysteresis*, CRSC Technical Report CRSC-TR99-1; Journal of Intelligent Material Systems and Structures, to appear.
- [12] R.C. SMITH AND Z. OUNAIES, *A hysteresis model for piezoceramic materials*, ICASE Report 99-29; Proceedings of the ASME International Mechanical Engineering Congress and Exposition, Nashville, TN, November, 1999, to appear.
- [13] R.C. SMITH AND Z. OUNAIES, *A domain wall model for hysteresis in piezoelectric materials*, ICASE Report 99-52; Journal of Intelligent Material Systems and Structures, submitted.
- [14] G. TAO AND P.V. KOKOTOVIĆ, *Adaptive Control of Systems with Actuator and Sensor Nonlinearities*, John Wiley and Sons, New York, 1996.
- [15] X.D. ZHANG AND C.A. ROGERS, *A macroscopic phenomenological formulation for coupled electromechanical effects in piezoelectricity*, Journal of Intelligent Material Systems and Structures, 4 (1993), pp. 307-316.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY(Leave blank)	2. REPORT DATE January 2000	3. REPORT TYPE AND DATES COVERED Contractor Report		
4. TITLE AND SUBTITLE A model for assymetric hysteresis in piezoceramic materials		5. FUNDING NUMBERS C NAS1-97046 WU 505-90-52-01		
6. AUTHOR(S) Ralph C. Smith Zoubeida Ounaies				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Institute for Computer Applications in Science and Engineering Mail Stop 132C, NASA Langley Research Center Hampton, VA 23681-2199		8. PERFORMING ORGANIZATION REPORT NUMBER ICASE Report No. 2000-1		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Langley Research Center Hampton, VA 23681-2199		10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA/CR-2000-209837 ICASE Report No. 2000-1		
11. SUPPLEMENTARY NOTES Langley Technical Monitor: Dennis M. Bushnell Final Report To appear in the Proceedings of the 1999 Fall Meeting of the Materials Research Society.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified-Unlimited Subject Category 64 Distribution: Nonstandard Availability: NASA-CASI (301) 621-0390		12b. DISTRIBUTION CODE		
13. ABSTRACT (Maximum 200 words) This paper focuses on the characterization of hysteresis exhibited by piezoelectric materials at moderate to high field levels. For soft materials in which dipoles are easily reconfigured, the hysteresis loop is observed to be rotationally symmetric about the zero field, zero polarization point and symmetric models can be employed. In harder materials, however, the loops are no longer rotationally symmetric which necessitates the development of commensurate characterization techniques. The model considered here is based upon the quantification of reversible and irreversible changes in polarization due to bending and translation of domain walls pinned at inclusions inherent to the materials. The performance of the model is illustrated through comparison with PZT4 data.				
14. SUBJECT TERMS hysteresis model, piezoceramic materials			15. NUMBER OF PAGES 11	
			16. PRICE CODE A03	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT	20. LIMITATION OF ABSTRACT	